

AD-A164 252


EPITAXIAL (100) GAAS THIN FILMS ON SAPPHIRE FOR SURFACE
ACOUSTIC WAVE/ELE (U) SPIRE CORP BEDFORD MA V E HAVEN
DEC 85 SPIRE-FR-60057 AFOSR-TR-86-0006 F49620-84-C-0108

1/1

UNCLASSIFIED

F/G 20/12

NL





MICROCOPY RESOLUTION TEST CHART
NBS-1963-A

AD-A164 252

DTIC FILE COPY

S **D**
ELECTE
FEB 12 1986

Approved for public release;
distribution unlimited.


spire

86 2 11 109

FR-60057
December 1985

EPITAXIAL (100) GaAs THIN FILMS ON
SAPPHIRE FOR SURFACE ACOUSTIC WAVE/ELECTRONIC DEVICES

Submitted to:
AFOSR
Directorate of Electronic and
Material Sciences
Bolling Air Force Base, WA 20332

AIR FORCE OFFICE OF SCIENTIFIC RESEARCH (AFSC)
NOTICE OF TRANSMITTAL TO DTIC
This technical report has been reviewed and is
approved for public release IAW AFR 190-12.
Distribution is unlimited.
MATTHEW J. KEMPER
Chief, Technical Information Division

Submitted by:
SPIRE CORPORATION
Patriots Park
Bedford, MA 01730

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER AFOSR-TR. 86-0006	2. GOVT ACCESSION NO. AD-A164153	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Epitaxial (100) GaAs Thin Films on Sapphire for Surface Acoustic Wave/Electronic Devices		5. TYPE OF REPORT & PERIOD COVERED Final Report 9/30/84.- 5/28/85
7. AUTHOR(s) Victor E. Haven, Jr.		6. PERFORMING ORG. REPORT NUMBER FR-60057
9. PERFORMING ORGANIZATION NAME AND ADDRESS Spire Corporation Patriots Park Bedford, MA 01730		8. CONTRACT OR GRANT NUMBER(s) F49620-84-C-0108
11. CONTROLLING OFFICE NAME AND ADDRESS Air Force Office of Scientific Research / NE Bolling AFB, DC		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 61102F
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) DCASMA Boston 495 Summer Street Boston, MS 02210-2184		12. REPORT DATE December 1985
		13. NUMBER OF PAGES 30
		15. SECURITY CLASS. (of this report) None UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Metalorganic chemical vapor deposition, gallium arsenide, surface acoustic wave devices, R-plane sapphire, y		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) In the past year it has been demonstrated that undoped <111> single crystal gallium arsenide could be grown on <0112> sapphire using the metalorganic chemical vapor deposition (MO-CVD) growth technique. An interesting and unexpected result from this work was that the GaAs films grown had a <111> orientation instead of the proposed <100> orientation. (continued)		

TABLE OF CONTENTS

<u>Section</u>		<u>Page</u>
1	INTRODUCTION	1-1
2	MO-CVD GROWTH SYSTEMS.	2-1
3	EXPERIMENTAL	3-1
3.1	Substrates	3-1
3.2	Deposition Studies	3-1
3.2.1	Deposition Temperature	3-1
3.2.2	Deposition Rate	3-7
3.2.3	As/Ga Ratio	3-9
3.2.4	Effects of Deposition Temperature on Orientation	3-9
4	MEASUREMENTS.	4-1
4.1	X-Ray Diffraction	4-1
4.2	Mobility	4-1
4.3	TEM	4-1
4.4	SIMS	4-5
4.5	Polaron C-V	4-5
5	SUMMARY.	5-1
6	REFERENCES	6-1
7	ASSOCIATED PERSONNEL	7-1

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	



LIST OF ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	MO-CVD Reactor With IBM-PC Control System	2-2
2	Schematic of MO-CVD Growth Chamber	2-3
3	Nomarski Micrographs of 6 Micron Polycrystalline GaAs Films Grown on $\langle 01\bar{1}2 \rangle$ Al_2O_3	3-3
4	Nomarski Micrographs of 6 Micron Highly Oriented (111) GaAs Films Grown on $\langle 01\bar{1}2 \rangle$ Al_2O_3	3-4
5	Nomarski Micrograph of 6 Micron (111) Single Crystal GaAs Film on $\langle 01\bar{1}2 \rangle$ Al_2O_3 Grown at 725°C	3-5
6	Laue Photograph of $\langle 01\bar{1}2 \rangle$ Al_2O_3	3-6
7	Nomarski Micrograph of 6-Micron Polycrystalline GaAs Film on Al_2O_3 Grown with Non-Optimum Conditions.	3-8
8	Nomarski Micrograph of 6-Micron Single Crystal GaAs Film Grown on Al_2O_3 With Optimum Conditions.	3-8
9	GaAs on Sapphire - Resistivity Measurement	4-2
10	TEM Micrographs of $\langle 111 \rangle$ GaAs Films on $\langle 01\bar{1}2 \rangle$ Al_2O_3	4-3
11	TEM Micrographs of Stacking Faults in 6-Micron GaAs Film Grown on $\langle 01\bar{1}2 \rangle$ Al_2O_3	4-4
12	SIMS Profile of a 6-Micron GaAs Film Grown on $\langle 01\bar{1}2 \rangle$ Al_2O_3	4-6

LIST OF TABLES

<u>Table</u>		<u>Page</u>
1	Growth Conditions to Deterine Optimum Deposition Temperature . . .	3-2
2	Two Temperature Deposition Process	3-2
3	Growth Conditions to Determine Optimum Deposition Rate	3-7
4	Growth Conditions to Determine Effect of As/Ga Ratio on Film Quality	3-9

SECTION I INTRODUCTION

This report covers the past years work on a program sponsored by U.S. Department of Defense to demonstrate that high-quality $\langle 100 \rangle$ GaAs/(01 $\bar{1}2$) sapphire (Al_2O_3) epitaxy could be achieved.

GaAs, with the $\langle 100 \rangle$ surface orientation, is preferred both for monolithic surface acoustic wave (SAW) and electronic device fabrication. The successful deposition of $\langle 100 \rangle$ GaAs/ $\langle 01\bar{1}2 \rangle$ Al_2O_3 is of great value because it would allow for the integration of SAW and electronic devices on a common chip.

Metalorganic chemical vapor deposition (MO-CVD) was used for all depositions during this work. Sapphire with an orientation of $\langle 01\bar{1}2 \rangle$ was chosen for the substrate, since its four-fold symmetry was expected to initiate $\langle 100 \rangle$ epitaxial growth. The quality of the GaAs films were characterized as a function of deposition temperature, As/Ga ratio and growth rate, in an attempt to optimize the deposition process.

The result that the films grown are of a $\langle 111 \rangle$ orientation, leads to the conclusion that the $\langle 01\bar{1}2 \rangle$ orientation of the Al_2O_3 does not appear to have a significant effect on determining the orientation of the films. This in turn leads to the belief that epitaxial GaAs films could be deposited on other types of substrates, such as quartz.

SECTION 2

MO-CVD GROWTH SYSTEMS

All GaAs depositions were performed in our second MO-CVD system which is also being used in a continuing program, funded by the Solar Energy Research Institute to fabricate GaAs/GaAlAs heteroepitaxial structures.

The MO-CVD reactor, shown in Figure 1, features a microprocessor control system and a rotating, vertical-geometry reaction chamber with a large growth area.

The MO-CVD growth chamber is shown schematically in Figure 2. The pyramid-shaped susceptor has a growth area of 100 cm^2 and can hold five 2" wafers per batch. A rotating thermocouple inside the RF-heated susceptor provides for feedback temperature control. The water-cooled fused-quartz vessel is sealed to the water-cooled stainless steel baseplate by means of a double O-ring arrangement. The rotating fused-quartz shaft is sealed to the baseplate by means of a custom-designed ferrofluid feedthrough.

The entire MO-CVD process sequence is controlled by a Westinghouse PC-900 programmable controller in conjunction with an IBM-PC resulting in a sophisticated computer control system. This system allows for maximum ease of operation, reproducibility, documentation capabilities, and continual monitoring of all safety conditions for operator safety.

The gas-delivery system consists of face-seal fittings and bellows valves butt-welded to stainless steel tubing. A palladium-alloy purifier is used in the hydrogen line and all flows are controlled by electronic mass flow controllers. A filtered-air cabinet is provided in the wafer-loading area and organometallic sources are maintained in temperature-stabilized cooling baths.

This MO-CVD reactor is designed to grow GaAs and GaAlAs over the entire alloy range. Maximum doping levels are mid- 10^{18} range for N-type and about 10^{19} for p-type GaAs. Growth rates can be varied from 0.01 to 2 $\mu\text{m}/\text{min}$ and the growth temperature is typically between 650°C and 800°C.



FIGURE 1. MO-CVD REACTOR WITH IBM-PC CONTROL SYSTEM.

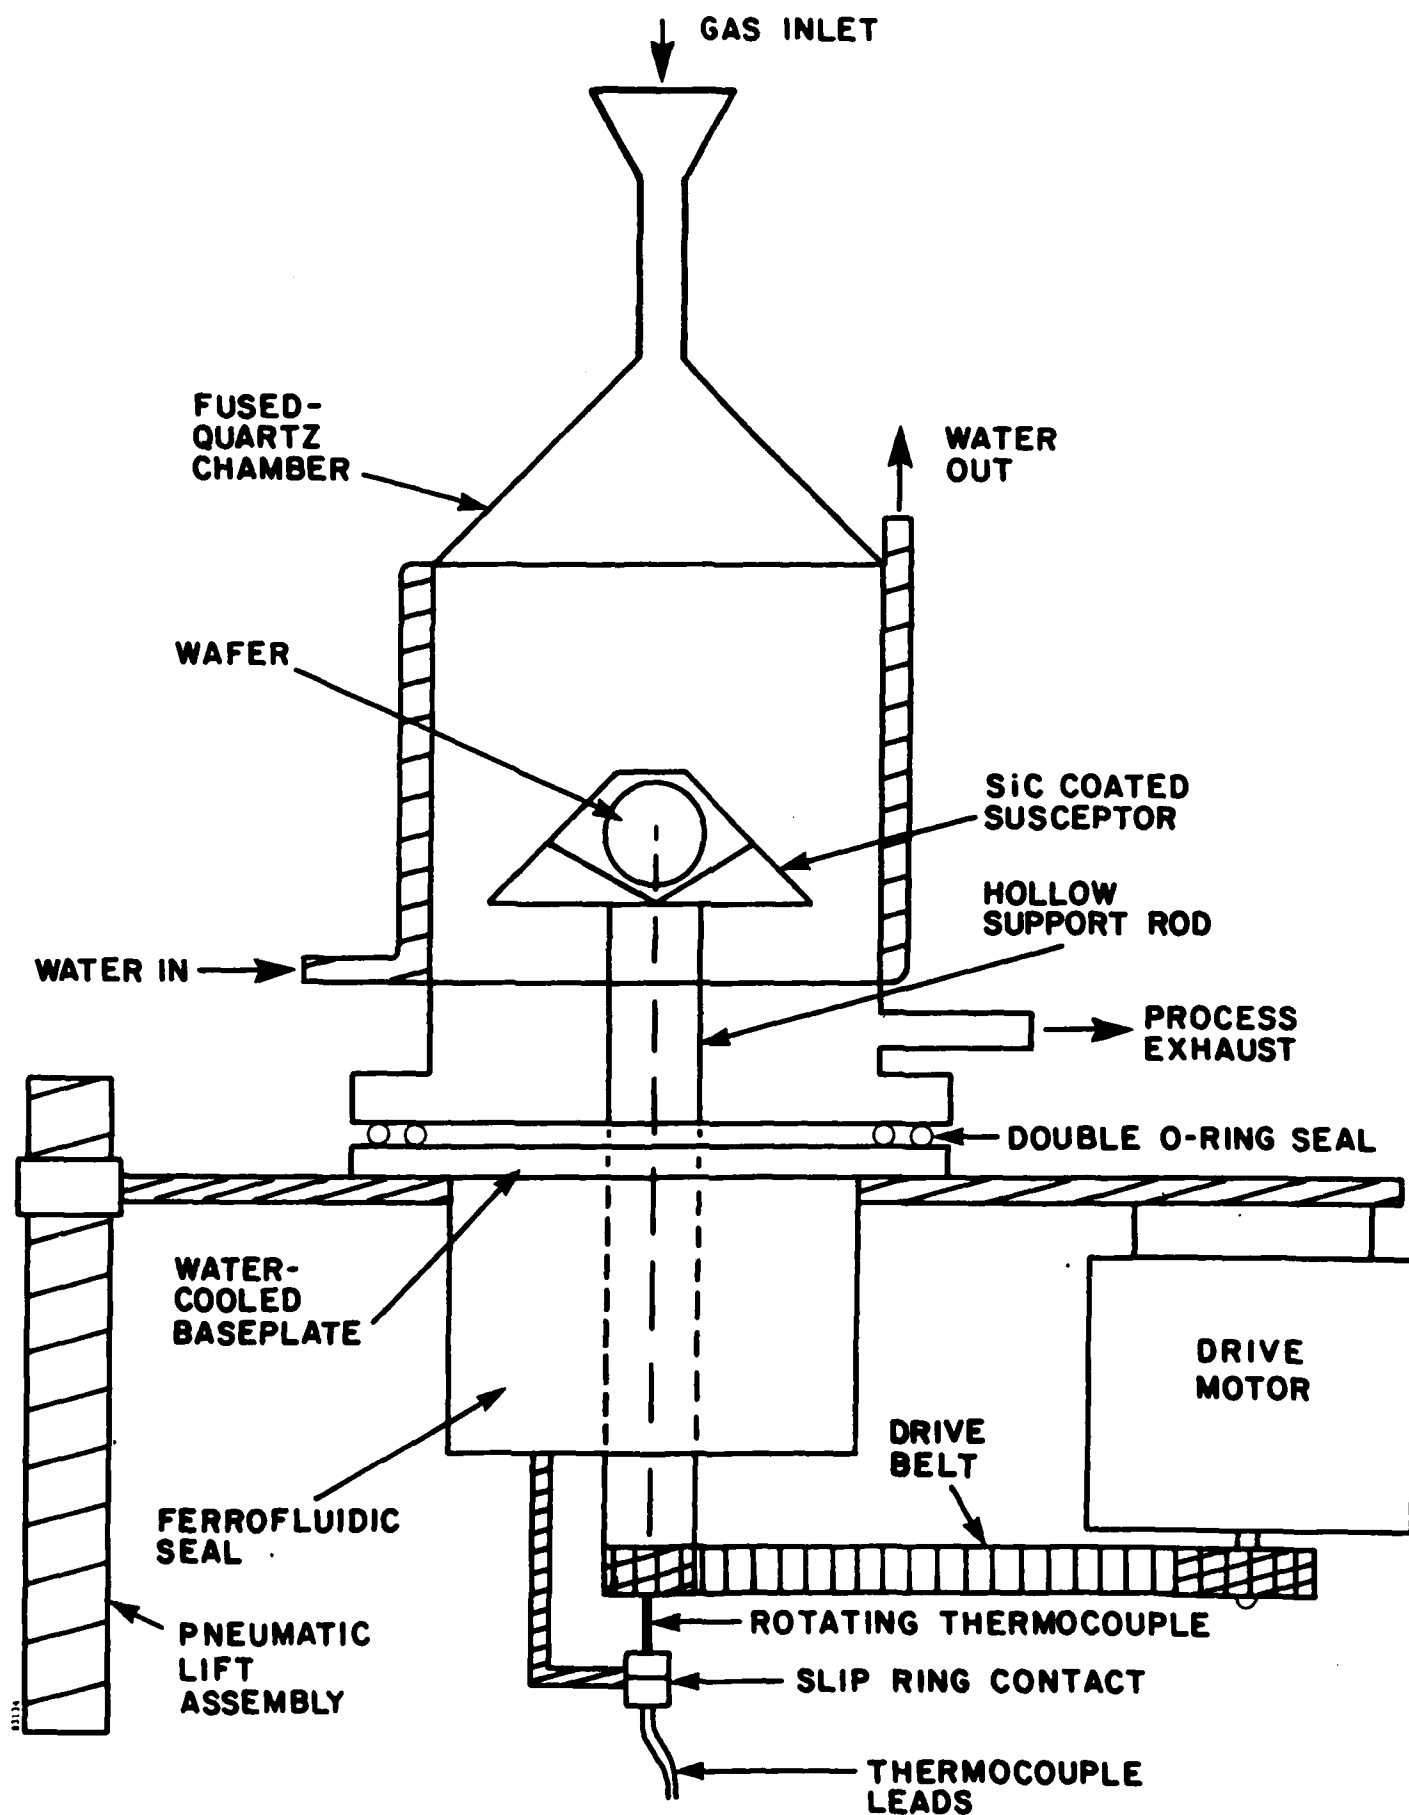


FIGURE 2. SCHEMATIC OF MO-CVD GROWTH CHAMBER.

SECTION 3 EXPERIMENTAL

3.1 SUBSTRATES

The sapphire (Al_2O_3) substrates used for this work were supplied by Saphikon.⁽²⁾ They were all $\langle 01\bar{1}2 \rangle \text{Al}_2\text{O}_3$ cut in 1" x 1" squares with the front side polished to EPI quality and the back side polished to an optical finish. Before loading, the substrates were cleaned in acetone and methanol followed by a DI rinse. The substrates were then cleaned in $\text{NH}_4\text{OH}:\text{H}_2\text{O}_2:\text{H}_2\text{O}, 2:1:10$ for 30 seconds. Each sample was dipped in HF and rinsed just prior to loading. A small piece of N^+GaAs was also loaded each run for evaluation.


3.2 DEPOSITION STUDIES

Experiments were designed to determine the best conditions for the deposition of GaAs on $\langle 01\bar{1}2 \rangle \text{Al}_2\text{O}_3$. The growth parameters studied were deposition temperature, As/Ga ratio and deposition rate. The deposited layers were evaluated and characterized in terms of surface morphology, electronic quality and structural perfection.


3.2.1 Deposition Temperature

The first growth experiments were done to determine the optimum deposition temperature. A series of runs were made at a fixed growth rate and As/Ga ratio while the temperature was varied for each run. A 6-micron thick undoped layer was deposited at each temperature. The growth conditions are shown in Table 1.


Each sample was evaluated by eye, Nomarski phase-contrast microscopy and by a Sloan Dektak surface profiler. The samples grown at 600°C, 620°C, 650°C all have a dull mat-gray appearance to the eye and look polycrystalline when viewed by the Nomarski microscope (Figure 3). The samples grown at 675°C, 700°C, 725°C, and 750°C all have a smooth, reflective surface to the eye. The samples grown at 675°C, 700°C, and 750°C when viewed by microscopy, reveal a large grain texture (Figure 4). The surface of the sample grown at 725°C has a very definite crystalline appearance as can be seen by the triangular morphology in Figure 5.

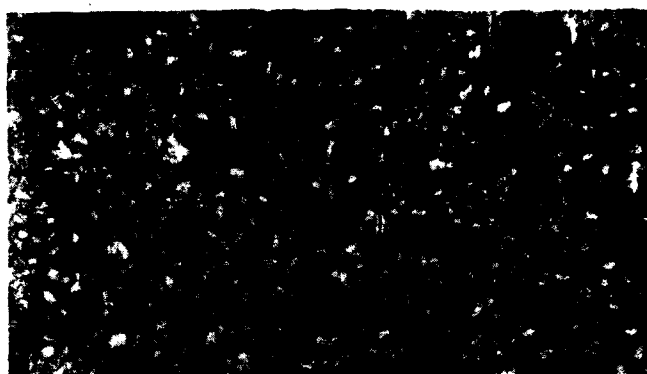

(a) 600°C




(b) 620°C

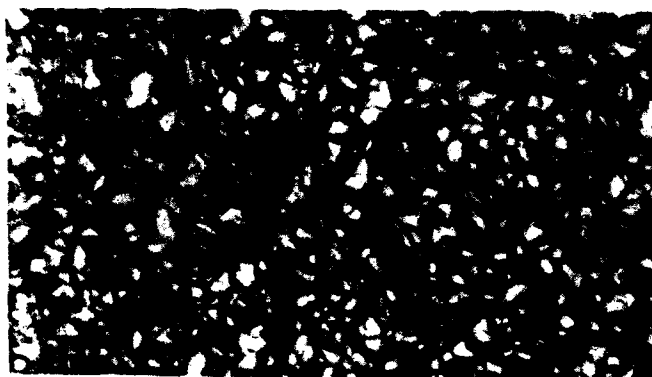

(c) 650°C

FIGURE 3.

NOMARSKI MICROGRAPHS OF 6 MICRON POLY-CRYSTALLINE GaAs FILMS GROWN ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 .

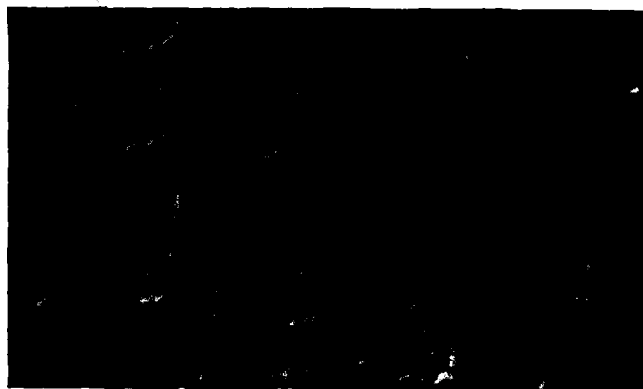

10 μ m

(a) 675°C



(b) 700°C



(c) 750°C

FIGURE 4. NOMARSKI MICROGRAPHS OF 6 MICRON HIGHLY ORIENTED (111) GaAs FILMS GROWN ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 .



10 μ m

FIGURE 5. NOMARSKI MICROGRAPH OF 6 MICRON (111) SINGLE CRYSTAL GaAs FILM ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 GROWN AT 725°C.

The sample grown using the two step process is mat-gray and appeared polycrystalline with

Selected samples sent to Manlabs³ for x-ray diffraction analysis. GaAs layers are oriented in the (111) direction. Samples grown at 650°, 675°, 700°, 725° all show a (333) reflection indicating a highly oriented

The sample indicating this sample is somewhat polycrystalline.

The sample, Manlabs, revealed a slightly sharper (111) peak which probably indicates less strain in the crystal.

The Al_2O_3 substrate was also examined by x-ray diffraction and a laue photograph (Figure 6) which verified it was $\langle 01\bar{1}2 \rangle \text{Al}_2\text{O}_3$ as expected.

FIGURE 6. LAUE PHOTOGRAPH OF $\langle 01\bar{1}2 \rangle \text{Al}_2\text{O}_3$.

After examining the data from Manlabs, comparing photographs from the microscope, examining the samples by eye and comparing Dektak measurements, it was concluded that the sample grown at 725° gave the best crystal. A highly oriented <111> GaAs layer with an average surface roughness of .5 microns.

3.2.2 Deposition Rate

A second series of growth experiments were done to determine how the deposition rate effected the films. 725° was the temperature chosen for this series of experiments because it yielded the best crystal in the first series. The As/Ga ratio was kept constant. Table 3 shows the growth conditions.

TABLE 3. GROWTH CONDITIONS TO DETERMINE OPTIMUM DEPOSITION RATE

Run #	Deposition Rate	As/Ga Ratio	Deposition Temperature	Layer Thickness
1	5.5Å/sec	10:1	725°C	6 μm
2	22Å/sec	10:1	725°C	6 μm
3	44Å/sec	10:1	725°C	6 μm

Samples were again examined and evaluated by eye and by microscopy. All samples other than the one grown at 22Å/sec appeared polycrystalline when viewed by microscopy (Figure 7) and had the same mat-gray appearance by eye. The sample grown at 22Å/sec again appeared to be crystalline (Figure 8) and have a bright reflective surface as before.


The above experiments led to the conclusion that the GaAs film quality is very depended on the deposition rate. The optimum growth conditions after completing the first two series of runs was deposition temperature 725°C, AsGa ratio 10:1 and deposition rate of 22Å/sec.



10 μ m

FIGURE 7.

NOMARSKI MICROGRAPH OF 6-MICRON POLY-CRYSTALLINE GaAs FILM ON Al₂O₃ GROWN WITH NON-OPTIMUM CONDITIONS.

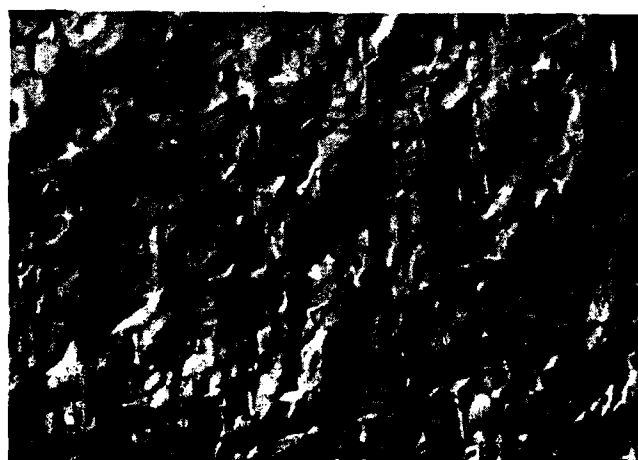

10 μ m

FIGURE 8.

NOMARSKI MICROGRAPH OF 6-MICRON SINGLE CRYSTAL GaAs FILM GROWN ON Al₂O₃ WITH OPTIMUM CONDITIONS.

3.2.3 As/Ga Ratio

A third series of runs were done to determine how the As/Ga ratio would effect the film quality.

Two runs were made at the optimum temperature of 725° and growth rate of 22Å/sec. The growth conditions are shown in Table 4.

TABLE 4. GROWTH CONDITIONS TO DETERMINE EFFECT OF
As/Ga RATIO ON FILM QUALITY

Run #	Deposition Rate	As/Ga Ratio	Deposition Temperature	Layer Thickness
1	22 Å/sec.	20:1	725°C	6 μm
2	22 Å/sec.	5:1	725°C	6 μm

Samples grown at both the above As/Ga ratios are mat-gray and looked polycrystalline under the microscope.

3.2.4 Effects of Deposition Temperature on Orientation

One run was made to determine if a high deposition temperature would possibly enhance $\langle 100 \rangle$ growth due to the high energy level of the GaAs atoms. The run was made at 825°C with optimum growth conditions (deposition rate=22Å/sec, As/Ga ratio=10:1). This sample also looks mat-gray and polycrystalline by microscopy.

SECTION 4 MEASUREMENTS

4.1 X-RAY DIFFRACTION

Selected samples were again sent to Manlabs for x-ray diffraction. Along with the GaAs/(0112) samples, one GaAs/0001 Al_2O_3 sample was also sent. This sample was grown during one of the runs with optimum growth conditions and was used as a comparison. $\langle 0001 \rangle$ Al_2O_3 is known to initiate $\langle 111 \rangle$ GaAs growth from previous work done at Spire which was funded by industry and has been reported elsewhere.⁽¹⁾ Data from Manlabs reinforced the first findings that the sample grown at the optimum settings of 725°, AsGa ratio 10:1 and deposition rate of 22 Å second is the best crystal. They concluded that this sample is a single crystal layer with a $\langle 111 \rangle$ orientation. It was also found that there is very little difference if any between the layer grown on $\langle 0001 \rangle$ Al_2O_3 and $\langle 0\bar{1}12 \rangle$ Al_2O_3 both layers are $\langle 111 \rangle$ single crystal GaAs.

The best samples were then chosen for closer examination. Electronic qualities were attempted to be measured by Hall effect measurement. Defect populations were examined by transmission electron microscopy (TEM). The purity and autodoping were investigated by secondary ion mass spectroscopy (SIMS). A measurement of the doping level was attempted by Polaron C-V profilometry.

One sample was used for all the above measurements. The sample used was grown at the optimum conditions, 725°C, As/Ga ratio=10:1 and growth rate of 22Å/sec. It was sectioned as needed for each measurement.

4.2 MOBILITY

A mobility measurement was attempted by Hall effect. This proved to be unsuccessful due to the fact that the resistivity (ρ) of the layer is too high (Figure 9) for our Hall setup, which is sensitivity limited by its small magnet.

4.3 TEM

A section was sent to ARACOR⁽⁴⁾ for examination by TEM. ARACOR verified that the crystal is a (111) crystal, however they did detect some evidence of polycrystallinity.

Sample: Van der Pauw Hall configuration

ICM X ICM

Room light only

$$\frac{V}{I} = \frac{10V}{10nA} = 10^9$$

$$RSH = 4.53 \frac{V}{I} = 4.53 \times 10^9$$

$$= Rsh \cdot t = 2.27 \times 10^6$$

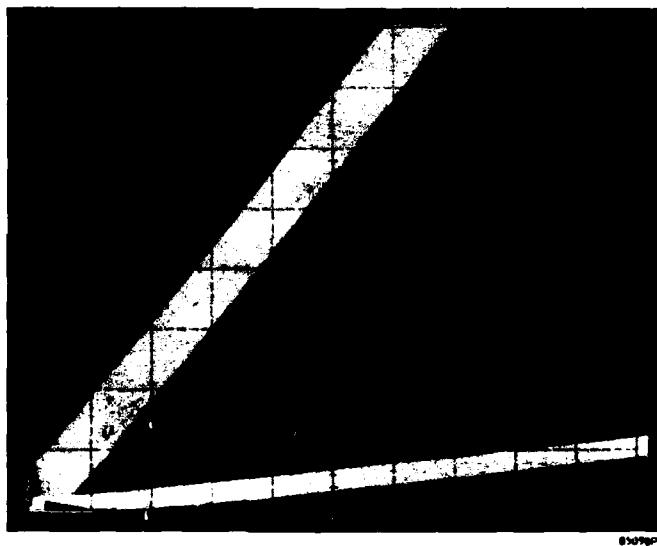


FIGURE 9. GaAs ON SAPPHIRE - RESISTIVITY MEASUREMENT. Top Illuminated, Bottom Dark.

Figure 10 A and B shows a grain which is of a different orientation than the surrounding $\langle 111 \rangle$ region. As can be seen, the grain is rotated with respect to the matrix. This is also confirmed by the extra non-symmetric spot in the laue photograph (Figure 10A). Aracor was not able to determine the orientation of this grain. The sample also has a high density of stacking faults around 10^7 cm^{-2} calculated from the micrographs (Figure 11 A and B).



FIGURE 10-A.



FIGURE 10-B. TEM MICROGRAPHS OF $\langle 111 \rangle$ GaAs FILM ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 .



FIGURE 11-A.




FIGURE 11-B. TEM MICROGRAPHS OF STACKING FAULTS IN 6-MICRON GaAs FILM GROWN ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 .

4.4 SIMS

Another section was sent to Northern Analytical Lab⁵ for examination by SIMS. A depth-profile was taken through the GaAs layer into the Al_2O_3 substrate. The profile (Figure 12) shows the plots for As, Ga, Al, C, Si and K. As can be seen there is an Al spike at the GaAs/ Al_2O_3 interface which quickly disappears early into the GaAs layer. Northern Analytical believes that the Al spike in the GaAs layer is not actually there, but was just an artifact of the measurement due to a charge build up at the surface of the Al_2O_3 . The Al in the first portion of the GaAs film is believed to be real and quickly dissipates as mentioned above.

4.5 POLARON C-V

An attempt was made to measure the carrier concentration of the best film using a Polaron profile plotter. The carrier concentration is calculated from the capacitance-voltage data taken from a Schottky barrier formed between the GaAs film and an electrolyte solution. Omic contact must be made either to the back of the substrate or to the deposited film in order for the Polaron to operate. Due to the insulating nature of the Al_2O_3 substrate and the highly resistive grown layer, omic contact could not be achieved so the carrier concentration could not be measured.

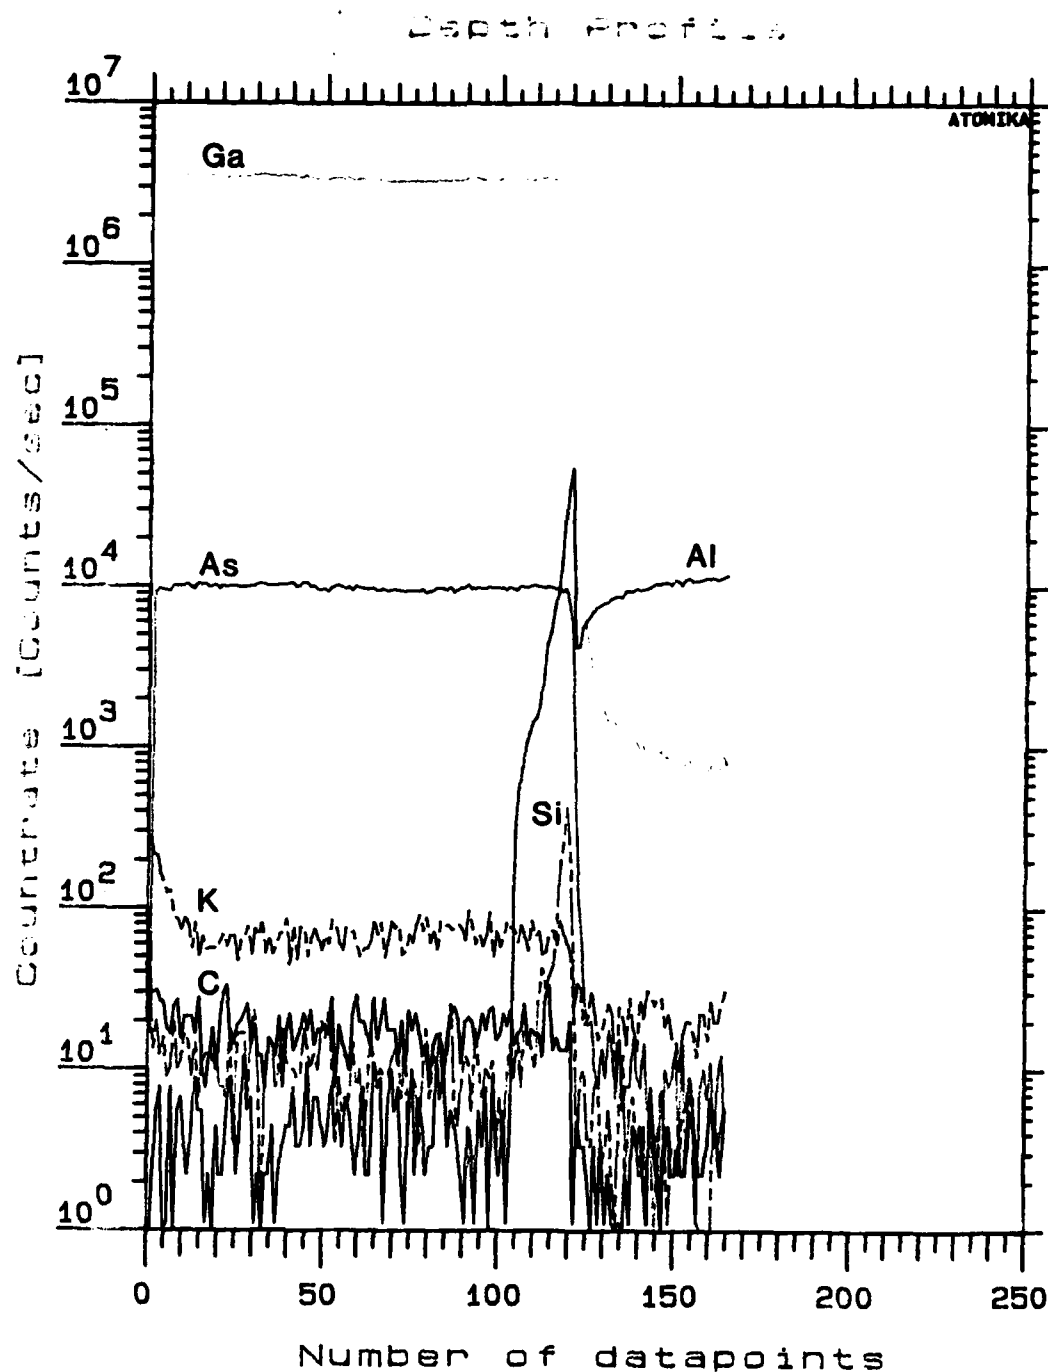

Primary Ions :	Oxygen	Label	Mass	Energy	Cycles
Ion Energy :	12 [kev]	AS	75.0	-5.0	5
Beam Current :	500 W/CC [nA]	AL	43.0	-5.0	5
Scan Width :	0.400 [mm]	GA	71.0	-5.0	2
Scan Speed :	2 [s/Frame]	C	12.0	-5.0	5
Scan Gate :	30 [%]	SI	28.0	-5.0	5
		K	39.0	-5.0	5

FIGURE 12. SIMS PROFILE OF A 6-MICRON GaAs FILM GROWN ON $\langle 01\bar{1}2 \rangle$ Al_2O_3 .

SECTION 5

SUMMARY

The conclusions, observations and results of the past year are as follows:

1. A reproducible process for depositing $\langle 111 \rangle$ single crystal GaAs on $\langle 01\bar{1}2 \rangle$ Al_2O_3 has been developed using the MO-CVD technique. The reason for the films being of $\langle 111 \rangle$ orientation instead of the proposed $\langle 100 \rangle$ orientation must still be investigated.
2. The $\langle 01\bar{1}2 \rangle$ orientation of the Al_2O_3 substrate did not appear to have a significant effect on determining the $\langle 111 \rangle$ orientation of the GaAs films.
3. The best films grown are highly reflective to the eye and have a surface roughness of approximately .4 microns.
4. Deposition temperature, GaAs ratio and deposition rate, all affected the quality of the films.
5. The defect density of the films is approximately 10^7 cm^{-2} . More work is needed to improve the films.
6. The SIMS profile showed very little autodoping or contamination in the GaAs films attributed to the Al_2O_3 substrate.

SECTION 6
REFERENCES

- 1) H.M. Manasevit, Journal of Crystal Growth, 22, (1974), pp.125-148.
- 2) Saphikon, 51 Powers Street, Milford, NH 03055
- 3) Manlabs, 21 Erie Street, Cambridge, MA
- 4) ARACOR, 1223 East Arques Avenue, Sunnyvale, CA 94086
- 5) Northern Analytical Lab, Inc., 3 Northern Blvd., B2, Amherst, NH 03031

SECTION 7
ASSOCIATED PERSONNEL

ROBERT G. WOLFSON

EDUCATION: B.S., Metallurgy, M.I.T.
 M.S. and Ph.D., Materials Science, Northwestern University

PROFESSIONAL EXPERIENCE:

Present Spire Corporation. Vice President/Research. Dr. Wolfson directs R&D on materials and processes for photovoltaics, solid-state micro-electronics, and transducer/detector technology. He is also responsible for managing Spire's research programs from the U.S. Departments of Defense and Energy and from private industry. Current activities center upon the elemental and compound semiconductors: silicon (both crystalline and amorphous), germanium, and the III-V and II-VI compounds; there are, in addition, major efforts on other materials, such as amorphous beryllium and cubic (adamantine) boron nitride. The chief applications for this work are in the areas of thin-film solar cells, discrete devices and integrated circuits, microwave communications, infrared imaging and optics, fiber optics, and protective coatings for wear and chemical resistance.

Prior to 1979 Before joining Spire, Dr. Wolfson was Manager, Advanced Materials Equipment for the Varian/Lexington Vacuum Division and earlier was Associate Director, Materials Technology Center, General Instrument Corporation. For six years, he served as Associate Professor of Engineering at Dartmouth College; still earlier, he was Project Leader, Epitaxy Research at P.R. Mallory Company and Manager, Materials R&D at Sylvania Semiconductor Division, where he began his career.

PUBLICATIONS:

"Rapid Diffusion of Molybdenum Trace Contamination in Silicon" (with S. P. Tobin, A.C. Greenwald, D. L. Meier, and P. J. Drevinsky), to be published in Materials Research Society Proceedings.

"A Study of Ion Implantation and Annealing of Low-Cost Silicon Sheet" (with M. B. Spitzer and C. J. Keavney), Record of the 17th IEEE Photovoltaic Specialists Conference, 252-258 (1984).

"Heteroepitaxial (Al,Ga)As Structures on Ge and Si for Advanced High Efficiency Solar Cells" (with S.M. Vernon, M.B. Spitzer, and S. P. Tobin), Record of the 17th IEEE Photovoltaic Specialists Conference, 434-439 (1984).

"Development of GaAs/Si and GaAlAs/Si Monolithic Structures for Future Space Solar Cells (with M.B. Spitzer, S. M. Vernon, and S. P. Tobin), Record of the NASA Space Photovoltaics Research and Technology Conference, Cleveland (1983).

ROBERT G. WOLFSON (Continued)

"Ion Beam Synthesis of Cubic Boron Nitride" (with S. Shanfield), J. Vac Sci. Technol. A1, 323 (1983).

"Ion Implanted Junctions for Silicon Space Solar Cells" (with M. B. Spitzer and M. M. Sanfacon), Record 18th Intersociety Energy Conversion Engineering Conference, 1213 (1983).

"Photovoltaic Technology," in Photonics, Book II, 29th edition, Optical Publishing Company, Pittsfield, MA, PpE 152-154 (1983).

"A New Electron Beam Polishing Technique for Heteroepitaxial Thin Films" (with S.P. Tobin, A.C. Greenwald, and T.T. Wong), in Laser and Electron-Beam Interactions with Solids, B.R. Appleton and G.K. Celler, eds. (Elsevier Science Publishing Company, New York, 1982), pp 725-730.

"Pulsed Electron Beam Processing of Silicon" (with A.C. Greenwald, R.G. Little, and M.B. Spitzer), in Laser and Electron-Beam Interactions with Solids, B.R. Appleton and G.K. Celler, eds. (Elsevier Science Publishing Company, New York, 1982), pp 621-626.

"Ion-implanted Thin-film Solar Cells on Sheet Silicon" (with R.G. Little), Record of the 15th IEEE Photovoltaic Specialists Conference, 595-597 (1981).

"Low Temperature Deformation of Crystalline Nonmetals", in Plastic Deformation of Materials, R.J. Arsenault, ed. (Academic Press, New York, 1975), pp. 333-392.

"Growth of NaCl-KCl Mixed Crystals from the Melt" (with W. Kobes), Mater. Res. Bull. 2, 263-267 (1967).

"Anomalous Unconstrained Crystal Growth of GaAs" (with A.G. Lapierre and E.M. Juleff), in Crystal Growth, H.S. Peiser, ed. (Pergamon Press, New York, 1967), pp. 301-304.

"The Analysis of Berg-Barrett Skew Reflections and Their Application in the Observation of Process-Induced Imperfections in (111) Silicon Wafers" (with E.M. Juleff and A.G. Lapierre), in Advances in X-ray Analysis, Vol. 10 (Plenum Press, New York, 1967), pp. 173-184.

"Precipitation in NaCl-KCl Mixed Crystals" (with W. Kobes and M.E. Fine), J. Appl. Phys. 37, 704-712 (1966).

"The Observation of Lomer-Cottrell Dislocations in Boron-Diffused (111) Silicon by Berg-Barrett Skew Reflections" (with E.M. Juleff and A.G. Lapierre), Int. J. Electron. 21, 37-49 (1966).

"Observation of Locally Diffused Regions in Silicon Wafers by Berg-Barrett X-ray Diffraction Micrography" (with E.M. Juleff), J. Appl. Phys. 37, 2178-2179 (1966).

"Silicon/Corundum Epitaxy" (with J.L. Porter), J. Appl. Phys. 36, 2746-2751 (1965).

"Epitaxial Vapor Deposition of Ge onto CaF₂ from GeH₄" (with J.L. Porter), J. Appl. Phys. 36, 3690-3691 (1965).

VICTOR E. HAVEN

STAFF RESEARCHER

EDUCATION: A.S. and B.S., Electronic Engineering Technology, Wentworth Institute of Technology, 1978

PROFESSIONAL EXPERIENCE:

1978-Present Spire Corporation. Research Scientist. Responsible for: (1) MO-CVD of GaAs/GaAlAs for various research programs, (2) Lab supervision. Previously, as Process Engineer, designed software control for MO-CVD reactor product line. Wired, programmed, operated and maintained first MO-CVD reactor. Other experience with photolithographic processes for solar cells.

STANLEY M. VERNON

STAFF RESEARCHER

EDUCATION: M.S., Electrical Engineering, Rutgers University, 1976
B.S. cum laude, Physics, Boston College, 1972

PROFESSIONAL EXPERIENCE:

1981-Present Spire Corporation. Manager, Epitaxial R&D. Responsible for: (1) design and development of metalorganic chemical vapor deposition (MO-CVD) systems product line, (2) establishment and operation of MO-CVD GaAs/GaAlAs epitaxial growth service, and (3) GaAs/GaAlAs deposition for various research programs concerned with high-efficiency, thin-film solar cells for flat-plate and concentrator applications.

1976-1981 IBM Thomas J. Watson Research Center. Associate Engineer. Responsible for the chemical-vapor-deposition portion of the GaAs-GaAlAs research effort on solar cells and MESFETS. Designed and built an organometallic-CVD growth system. Successfully grew high-quality GaAs and GaAlAs layers, and produced first vapor-grown GaAs-GaAlAs solar cell and GaAs MESFET at IBM. Fabricated and tested Schottky barrier solar cells on Si and on single- and polycrystalline GaAs films. Developed recrystallization process which increased grain size of poly-GaAs films by three orders of magnitude. Achieved large-grained GaAs films on Si and SiO₂ by graphoeptaxy.

1974-1976 Rutgers University. Research Fellow, Electrical Engineering Department. Designed, fabricated and tested Schottky barrier (MIS) solar cells on Si. Discovered means of achieving reproducibly high open-circuit voltages by control of fabrication parameters.

1972-1974 Rutgers University. Research Assistant, Physics Department. Performed research on homogeneous nucleation in a fluid mixture.

STANLEY M. VERNON (Concluded)

1970-1971 Boston College. Research Assistant, Physics Department. Studied thermal annealing of radiation-damaged Si solar cells.

PUBLICATIONS:

"Growth of Epitaxial GaAs Films on Silicon Substrates," S. M. Vernon, S. Shanfield, and R. G. Wolfson, (submitted).

"Development of GaAs/Si and GaAlAs/Si Monolithic Structures for Future Space Solar Cells," M. B. Spitzer, S. M. Vernon, R. G. Wolfson, and S. P. Tobin, Proc. of the NASA SJsace Photovoltaic Research & Technology Conference, Cleveland, OH, October 1983.

"Progress Toward Development of High Efficiency GaAs Solar Cells on Silicon Substrates," S. M. Vernon, S. P. Tobin, and R. G. Wolfson, Proc. of the SERI 5th Annual Photovoltaic Advanced Research & Development Meeting, Denver, CO, May 1983.

"Growth of Epitaxial GaAs Films on Silicon Substrates," S. M. Vernon, S. Shanfield, and R. G. Wolfson, The Electrochemical Society Meeting, Recent News Abstracts, San Francisco, May 1983.

"Growth of Single-Crystal Ge-on-Si Substrates for GaAs Solar Cells," S. M. Vernon and S. P. Tobin, Abstracts of the Electronic Materials Conference, Fort Collins, CO, June 1982.

"Preparation of Silicon Substrates for GaAs Solar Cells by Electron Beam Pulse Processing," S. M. Vernon, Proc. of the SERI Advanced High-Efficiency Program Review Meeting, golden, CO, March, 1982.

"Grain Size and Its Fluence on Efficiency in Polycrystalline GaAs Solar Cells", A. E. Blakeslee and S. M. Vernon, Solar Cells 1, 81 (1979).

"Solar Cells on Large-Grain GaAs Thin Films", S. M. Vernon, A. E. Blakeslee and H. J. Hovel, J. Electrochem. Soc. 126, 703 (1979).

"Growth of Polycrystalline GaAs for Solar Cell Applications", A. E. Blakeslee and S. M. Vernon, IBM J. Res. Dev. 22, 346 (1978).

"Schottky Solar Cells on Thin Epitaxial Silicon", W. A. Anderson, S. M. Vernon, P. Mathe and B. Lalevic, Solid-State Electron. 19, 973 (1976).

"Factors Which Maximize the Efficiency of Cr-p-Si Schottky (MIS) Solar Cells", W. A. Anderson, S. M. Vernon, A. E. Delahoy, J. K. Kim and P. Mathe, J. Vac. Sci. Technol. 13, 1158 (1976).

"Temperature Effects in Schottky Barrier Solar Cells", S. M. Vernon and W. A. Anderson, Appl. Phys. Lett. 26, 707 (1975).

"Homogeneous Nucleation in a Critical Binary Fluid Mixture", J. S. Huang, S. M. Vernon and N. C. Wong, Phys. Rev. Lett. 33, 140 (1974).

JOHN J. ENTERKIN

MATERIALS RESEARCH DEVELOPMENT TECHNICIAN

PROFESSIONAL EXPERIENCE

- 1984-present Spire Corporation. Research Technician. Responsible for: (1) Operation and maintenance of MO-CVD reactor, (2) Design of GaAs/GaAlAs growth conditions for research programs.
- 1980-1984 MA/COM Corporation. Diffusion Technician. Responsible for Lab equipment, deposition and diffusion of silicon devices.

END

FILMED

3

-86

DTIC